



Semarak International Journal of Nanotechnology

Journal homepage:
<https://semarakilmu.my/index.php/sijn/index>
ISSN: 3030-6604



Subcritical Water Extraction of Banana Peel Derived ZnO for Photodegradation of Paracetamol

Lakshman Rao Sathiya Narayana¹, Mohamad Aizad Mohd Mokhtar¹, Roshafima Rasit Ali¹, Vekes Balasundram¹, Nurhamieza Md Huzir², Pramila Tamunaidu^{1,2,*}, Habibollah Younesi³

¹ Department of Chemical and Environmental Engineering, Malaysia-Japan International Institute of Technology (MJIIT), Universiti Teknologi Malaysia Kuala Lumpur, Jalan Semarak, 54100, Kuala Lumpur, Malaysia

² Malaysia-Japan Advanced Research Centre (MJARC), Eduhub Pagoh, Universiti Teknologi Malaysia Pagoh, 84600, Pagoh, Muar, Johor, Malaysia

³ Department of Environmental Science, Faculty of Natural Resources, Tarbiat Modares University, B.O. Box 46414-356, Tehran, Iran

ARTICLE INFO

Article history:

Received 3 June 2024

Received in revised form 1 August 2024

Accepted 13 August 2024

Available online 17 September 2024

Keywords:

Subcritical water (SCW) extraction;

Banana peel extract (BPE);

Photocatalysts

ABSTRACT

Rapid industrialization and growth have led to the emergence of pharmaceutical compounds in water sources. Therefore, a photocatalytic degradation of paracetamol (PCM) was studied using green catalyst i.e. banana peel extract-based zinc oxide (BZnO) photocatalyst. The catalysts were synthesized by incorporating ZnO with banana peels extract (BPE) extracted using subcritical water (SCW) process at various temperature range between 140–180°C and residence time from 15–45 mins. The produced BZnO photocatalysts were tested for photocatalytic degradation at fixed conditions of 10 ppm of PCM, a photocatalyst dosage of 0.1 g for 120 min. The degradation percentage of PCM was determined using Ultraviolet-Visible Spectroscopy (UV-Vis). The photocatalyst with the highest PCM degradation was then characterized using X-ray Diffraction (XRD) and Brunauer–Emmett–Teller (BET) surface area and pore analyser. Results showed that the highest percentage of PCM photodegradation was 28.20 % using ZnO incorporated with SCW extracted BPE at 140°C for 30 mins. The energy band gap of pure ZnO is calculated to be 3.370 eV, while the energy band gap of the BZnO drops down to 3.290 eV proving that BPE could act as a reducing agent. Further analysis of this BZnO showed the formation of pure nanoparticles with a hexagonal wurtzite crystal structure from its XRD patterns. Additionally, the BET surface area and total pore volume recorded were 20.5702 m²/g and 0.73188 cm³/g, respectively. Hence, green catalyst synthesized by incorporating ZnO and BPE has the potential to be utilized for pharmaceutical wastewater treatment.

1. Introduction

Wastewater contamination poses a significant global challenge, exacerbated by the presence of emerging contaminants (ECs) such as pharmaceutical residues, notably paracetamol (PCM). PCM, ubiquitous due to its household use, enters water sources through effluents from drug factories, hospitals, and households, contributing to environmental pollution as Endocrine Disruptive Compounds (EDCs) according to several authors [1,2]. Khan *et al.*, [3] reported that traditional

* Corresponding author.

E-mail address: pramila@utm.my

wastewater treatment methods like biological processes and adsorption are often inadequate for PCM removal due to the compound's complex structure and stability, resulting in secondary pollutants like sludge. Photocatalysis using Zinc Oxide (ZnO) has emerged as a promising technology for PCM degradation under sunlight or UV light, offering efficient pollutant removal without generating additional waste based on study conducted by Arumugam *et al.*, [4]. Green synthesis methods such as sol-gel and precipitation are gaining popularity for producing ZnO photocatalysts, minimizing chemical usage and enhancing environmental sustainability in pharmaceutical wastewater treatment according to Sekaran *et al.*, [5].

According to Tan [6], banana peels, abundant yet underutilized, are rich in phytochemicals and phenolics, making them valuable for applications such as nanoparticle synthesis. The disposal of banana peels as waste in landfills based on Vu *et al.*, [7], highlights the need for sustainable utilization strategies to address environmental concerns. Subcritical water (SCW) extraction has emerged as a promising green technology for extracting bioactive compounds from plant sources, including bananas, according to Cheng *et al.*, [8], due to its ability to maintain liquid water at temperatures and pressures below the critical point. Ishak *et al.*, [9] reports that this method offers advantages such as high extraction yields and quality without the use of organic solvents, making it suitable for extracting antioxidants and phenolic compounds from various natural matrices.

This study focuses on harnessing the potential of subcritical water (SCW) extraction for synthesizing zinc oxide (ZnO) nanoparticles using banana peel extract (BPE) as a green precursor. SCW extraction, operating at moderate temperatures and pressures, facilitates the extraction of bioactive compounds from waste biomaterials like banana peels, while also minimizing energy consumption and environmental impact. The synthesized ZnO photocatalysts hold promise for enhancing the photodegradation efficiency of PCM in wastewater, thereby addressing critical gaps in current wastewater treatment strategies. By exploring the synergy between SCW extraction and green synthesis techniques, this research aims to contribute novel insights into sustainable nanomaterial synthesis and advanced water treatment technologies.

2. Methodology

All chemicals used in the research were of analytical grade without the need for further purification. Aqueous solutions for all chemicals were prepared using deionized (DI) water. The cultivar of banana, Pisang Nangka were obtained from a banana fritters stall in Kuala Lumpur, Malaysia.

- a) Materials: Banana peels (Pisang Nangka), 99% purity of zinc nitrate hexahydrate ($\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$) and 500 mg of paracetamol (PCM).
- b) Banana peel preparation: The cultivar of banana was selected based on its skin color intensity, rated as C3 (more green than yellow) on the Von Loesecke scale (1950). After washing each banana peel with distilled water and peeling the remaining pulp, the peel was further rinsed with distilled water, was cut into pieces measuring approximately 1 cm by 1cm, and subsequently dried at 60°C for 15 hours.
- c) Subcritical water (SCW) extraction: The sample-to-water ratio of 1 to 2 was experimented where 50 g of banana peel was loaded with 100 mL of distilled water into the SCW reactor. The sample was heated at various temperatures (140, 160 & 180 °C) at different residence times (15, 30 & 45 minutes). The reactor was cooled once the extraction was completed.

Banana peel extract (BPE) was collected from the vessel and filtered. The supernatant was collected, dried at 60°C for 15 hours and stored in a zip-lock bag for further test.

- d) Green synthesis of zinc oxide: Green synthesis of ZnO via BPE followed a simple sol-gel and combustion technique. 15 mL of BPE was mixed with 3 g of Zn(NO₃)₂·6H₂O at 80 °C and stirred at 400 rpm until a gel-like formation produced. Then, the gel was calcined in a furnace for 1 hr at 600 °C and 50 °C/min. The produced white-colored ZnO powder was kept in sample vials for further use at room temperature.
- e) Photocatalytic degradation of paracetamol: A 10 ppm PCM solution with pH value of 6 was prepared. The initial concentration of the PCM solution was determined using UV-Vis. 0.1 g of the synthesized BZnO was mixed with the PCM solution and sonicated for 5 minutes. The resulting mixture was placed in a photocatalytic reactor and stirred in the dark for 40 minutes to achieve absorption-desorption equilibrium. Then, the UV light was activated for 2 hours, with samples taken every 10 minutes to be centrifuged and analyzed using UV-Vis. These steps were replicated for all the BZnO photocatalysts. The photodegradation percentage of PCM was calculated by using Eq. (1), where C and C₀ are final PCM concentration and initial PCM concentration respectively.

$$\text{Percentage Degradation (\%)} = \frac{C_0 - C}{C_0} \times 100\% \quad (1)$$

3. Results

3.1 Green Synthesis of Banana Based Zinc Oxide Nanoparticle

Interestingly, the green method of synthesis using plant sources have been found appropriate for the production of ZnO NPs due to its numerous health, environmental, economic, and medicinal benefits according to Hamrayev *et al.*, [10]. The green synthesis approach via a straightforward sol-gel method using banana peel extract (BPE) resulted in an effective fabrication of ZnO. The interaction of BPE with an aqueous solution of zinc nitrate hexahydrate results in the formation of a complex involving zinc ions (Zn²⁺) and a hydroxyl group within BPE. Subsequent heating of the mixture until evaporation takes place leads to the formation of a gel-like substance. The gel was then exposed to thermal decomposition at elevated temperature and Khorsand Zak *et al.*, [11] said that it is to facilitate the conversion of Zn²⁺ complexes to ZnO NPs. The chemical equation pathway for the green synthesized BZnO is shown in Eq. (2) and Eq. (3).



3.2 Photocatalytic Degradation of Paracetamol

ZnO photocatalysts with different SCW extraction conditions of temperature (140, 160 & 180 °C) and residence time (15, 30 & 45 minutes) were successfully synthesized using BPE. Results show that all the BZnO has better performance compared to the chemically synthesized ZnO as illustrated in Figure 1. Among all the samples, Z14-30 has the highest photodegradation of PCM (28.20%) where the BPE was extracted at SCW conditions of 140 °C for 30 minutes. Z14-15 to Z14-30 shows an increasing trend of photodegradation percentage but Z14-45 decreases down to 21.88%, indicating

the most optimum photocatalysts is Z14-30 at 140 °C. Another study by Yu *et al.*, [12] on the subcritical water extraction of phenolic compounds from XiLan olive fruit dreg reported that the phenolic yield increased with longer residence times up to 30 minutes, after which it started to decrease. This suggests that there is an optimal residence time for maximizing the extraction of phenolic compounds.

As for ZnO extracted at 180 °C, there is a gradual increment in the photodegradation percentage, showing potential for the subsequent residence time of 60 minutes to possess a higher percentage. This suggests that longer the residence time, higher concentration phytochemicals are being extracted out from sample. A study conducted by Zullaikah *et al.*, [13], on the subcritical water extraction of phenolic compounds from Moringa oleifera leaves found that increasing the residence time from 5 to 20 minutes resulted in a significant increase in the total phenolic content of the extracts. The authors concluded that longer residence times allowed for more efficient extraction and recovery of the phenolic compounds.

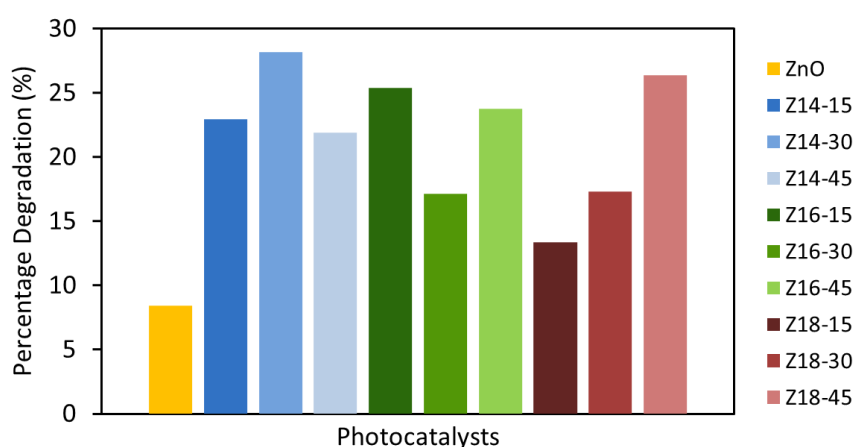


Fig. 1. Photodegradation of PCM with various photocatalysts

3.2 Ultraviolet-Visible Spectroscopy

The optical properties of the green synthesized BZnO were analysed by using UV-Vis spectroscopy. The optical band gap energy was evaluated for the photocatalysts, Z14-15, Z14-30 and Z14-45 by plotting Tauc's plot using the following Eq. (4).

$$(\alpha h\nu)^2 = A(h\nu - E_g) \quad (4)$$

where α , h , ν , E_g and A are the absorption coefficient, Planck's constant light frequency, band gap energy and a constant respectively. Through extrapolation of the linear of the linear portion (Figure 2), the intercept at x-axis will give the band gap value which are 3.285, 3.290 and 3.310 eV for Z14-15, Z14-30 and Z14-45 as reported in Table 1, respectively. The band gap indicates an increasing trend with the increase of residence time. This suggests that the synthesis reaction is time dependent. Previous study by Mokhtar *et al.*, [14] has reported band gap values for BZnO to be 3.230 eV. In comparison, commercial ZnO has a band gap energy of 3.370 eV according to Jafarova & Orudzhev, [15].

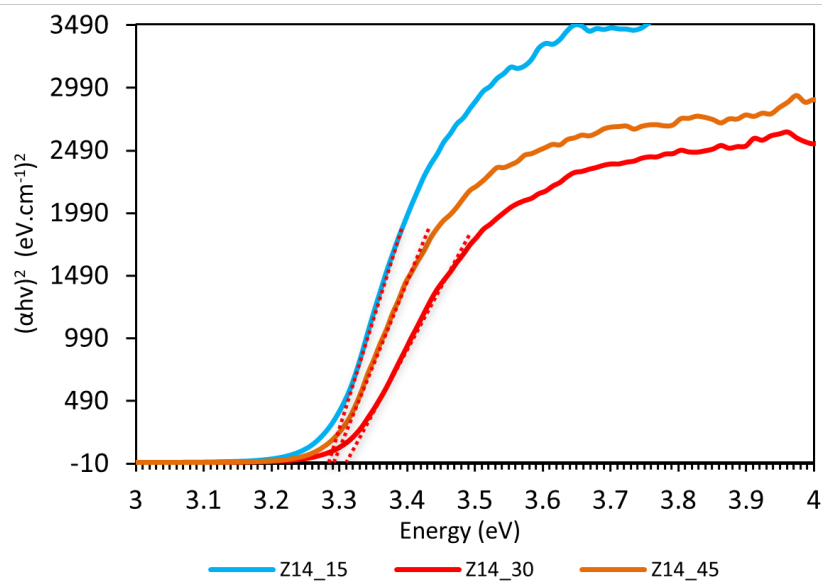


Fig. 2. Optical band gap energy

Table 1

Band gap energy of the green synthesized photocatalysts

Photocatalysts	Band gap energy (eV)
Z14-15	3.285
Z14-30	3.290
Z14-45	3.310

3.3 X-Ray Diffraction

The XRD pattern for Z14-30 is shown in Figure 3. Diffraction peaks of hexagonal wurtzite phase of Z14-30 represented at 31.72° (100), 34.54° (002), 36.21° (101), 47.46° (102), 56.72° (110), 63.89° (103), and 68.05° (201) planes corresponded to Joint Committee on Powder Diffraction Standards (JCPDS) card no. 36-1451 as per reported by Samuel *et al.*, [16]. However, there were two additional peaks observed (as indicated in blue) and this indicates that the synthesized ZnO NP are contaminated with impurities based on the study conducted by Gupta *et al.*, [17]. It can be deduced that the crystallinity of the sample is poor due to the broadness of the peaks and the intensity of the peaks were low. The crystallite size of Z14-30 can be calculated using the Scherrer formula as explained by Mursal *et al.*, [18] which is shown in Eq. (5), where D , k , λ , β and θ are denoted as average crystallite size, constant, full-width at half maximum (FWHM), wavelength and Bragg angle respectively.

$$D = \frac{0.9\lambda}{\beta \cos \theta} \quad (5)$$

By using the formula, the average crystallite size obtained for Z14-30 is 46.45 nm. According to Mohamed Isa [19], the increase of peak intensity reveals enhancement of crystallinity.

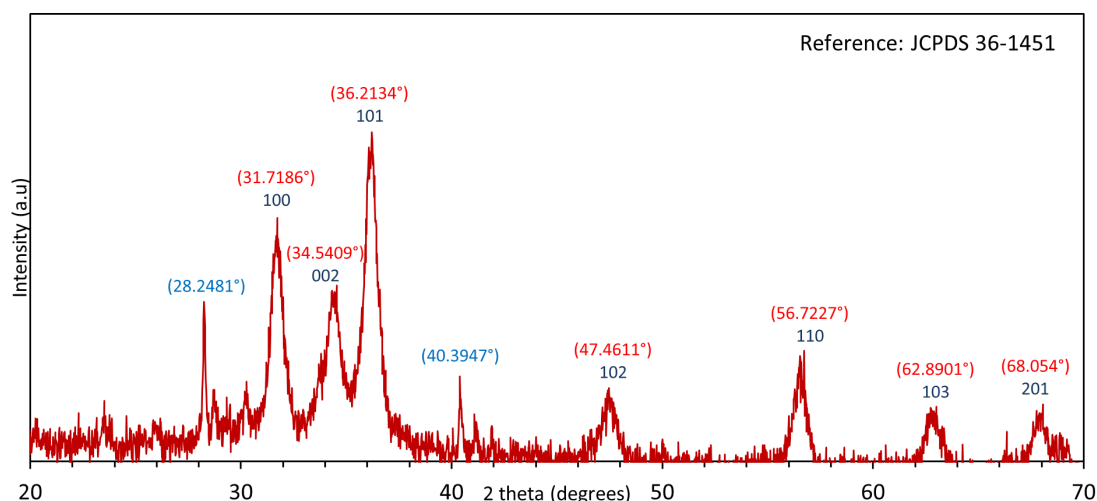


Fig. 3. XRD Pattern of synthesised Z14-30 photocatalysts

3.4 Surface Area and Pore Volume Analyzer

The surface area and pore characteristics of Z14-30 sample was determined using the Quantachrome Instrument Novatouch, with the Brunauer-Emmett-Teller (BET) and Barrett-Joyner-Halenda (BJH) models employed for surface area and pore volume calculations, respectively. According to the IUPAC classification, the isotherm exhibited by the sample, as presented in Figure 4 indicates Type IV isotherm and this shows the sample is mesoporous as reported by Thommes *et al.*, [20]. The condensed state interactions between molecules as well as the adsorbent-adsorptive interactions dictate the adsorption behaviour in mesopores. Pore condensation occurs in this instance after the first monolayer-multilayer adsorption on the mesopore walls, which follows the same path as the comparable portion of a Type II isotherm. The process by which a gas in a pore condenses to a liquid-like phase at a pressure p , that is lower than the bulk liquid's saturation pressure p_0 , is known as pore condensation based on Thommes & Cychosz [21]. The surface area and pore volume results are $20.5702 \text{ m}^2/\text{g}$ and $0.73188 \text{ cm}^3/\text{g}$ respectively.

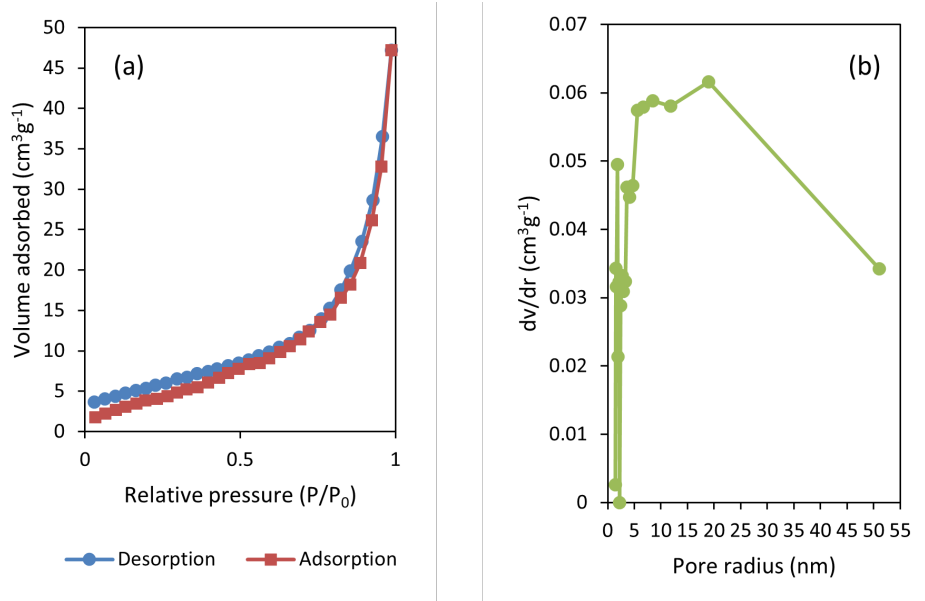


Fig. 4. Surface area and pore radius analysis for Z14-30. (a) Nitrogen adsorption-desorption isotherms. (b) Pore size distribution

4. Conclusions

The present study reveals that BPE-based zinc oxide was successfully synthesized at various SCW extraction conditions of temperature (140, 160 & 180 °C) and residence time (15, 30 & 45 minutes). The residence time shows more significant impact on the photocatalytic properties to degrade PCM under UVC light with the highest photodegradation percentage of 28.20% for BPE at 140 °C for 30 minutes which is much higher than the chemically synthesized ZnO. Therefore, the SCW extraction method proposed in this study has promises to be used for the green synthesis of BZnO NPs in the utilization of paracetamol photocatalytic degradation in wastewaters.

Acknowledgement

The authors would like to thank Malaysia-Japan International Institute of Technology (MJIT) for the funding and support of this project.

References

- [1] Khan, Shamshad, Mu Naushad, Muthusamy Govarthanan, Jibran Iqbal, and Sulaiman M. Alfadul. "Emerging contaminants of high concern for the environment: Current trends and future research." *Environmental Research* 207 (2022): 112609.
- [2] Abdel-Wahab, Aboel-Magd, Al-Sayed Al-Shirbini, Omima Mohamed, and Osama Nasr. "Photocatalytic degradation of paracetamol over magnetic flower-like TiO₂/Fe₂O₃ core-shell nanostructures." *Journal of Photochemistry and Photobiology A: Chemistry* 347 (2017): 186-198. <https://doi.org/10.1016/j.jphotochem.2017.07.030>
- [3] Khan, Sovann, Heechae Choi, Donghun Kim, Seung Yong Lee, Qiaohong Zhu, Jinlong Zhang, Seungchul Kim, and So-Hye Cho. "Self-assembled heterojunction of metal sulfides for improved photocatalysis." *Chemical Engineering Journal* 395 (2020): 125092. <https://doi.org/10.1016/j.cej.2020.125092>
- [4] Arumugam, Manikandan, Dinesh Babu Manikandan, Elayaraja Dhandapani, Arun Sridhar, Karthiyayini Balakrishnan, Manickavasagam Markandan, and Thirumurugan Ramasamy. "Green synthesis of zinc oxide nanoparticles (ZnO NPs) using *Syzygium cumini*: Potential multifaceted applications on antioxidants, cytotoxic and as nanonutrient for the growth of *Sesamum indicum*." *Environmental Technology & Innovation* 23 (2021): 101653. <https://doi.org/10.1016/j.eti.2021.101653>
- [5] Sekaran, Chitra, Dhanya Vishnu, Balaji Dhandapani, T. Alagesan, and G. Balaji. "Facile synthesis of zinc oxide nanoparticles using glycerol as cross-linker and the kinetic studies for the photocatalytic degradation of acid blue 113 dye." *Results in Chemistry* 4 (2022): 100377. <https://doi.org/10.1016/j.rechem.2022.100377>
- [6] Tan, B. C. "Can banana be a success story for Malaysia." *Journal of Agribusiness Marketing* 9, no. 1 (2022): 13-22. <https://doi.org/10.56527/jabm.9.1.2>
- [7] Vu, Hang T., Christopher J. Scarlett, and Quan V. Vuong. "Phenolic compounds within banana peel and their potential uses: A review." *Journal of functional foods* 40 (2018): 238-248. <https://doi.org/10.1016/j.jff.2017.11.006>
- [8] Cheng, Yan, Fumin Xue, Shuai Yu, Shichao Du, and Yu Yang. "Subcritical water extraction of natural products." *Molecules* 26, no. 13 (2021): 4004. <https://doi.org/10.3390/molecules26134004>
- [9] Ishak, Nur Akmal, Muhammad Yusuf Abdul Rashid, and Nur Athirah Zabidi. "Antidiabetic and antioxidant capacities of local banana peels extract by using subcritical water extraction technique." *Ulum Islamiyyah* 26 (2019): 19-30. <https://doi.org/10.33102/uij.vol26no.90>
- [10] Hamrayev, Hemra, Kamyar Shameli, and Serdar Korpayev. "Green synthesis of zinc oxide nanoparticles and its biomedical applications: A review." *Journal of Research in Nanoscience and Nanotechnology* 1, no. 1 (2021): 62-74. <https://doi.org/10.37934/jrnn.1.1.6274>
- [11] Zak, A. Khorsand, WH Abd Majid, M. R. Mahmoudian, Majid Darroudi, and Ramin Yousefi. "Starch-stabilized synthesis of ZnO nanopowders at low temperature and optical properties study." *Advanced Powder Technology* 24, no. 3 (2013): 618-624. <https://doi.org/10.1016/j.appt.2012.11.008>
- [12] Yu, Xue-mei, Ping Zhu, Qiu-ping Zhong, Meng-ying Li, and Han-ruo Ma. "Subcritical water extraction of antioxidant phenolic compounds from XiLan olive fruit dreg." *Journal of food science and technology* 52 (2015): 5012-5020. <https://doi.org/10.1007/s13197-014-1551-z>
- [13] Zullaikah, S., R. Y. Naulina, P. Meinawati, K. Fauziyah, M. Rachimoellah, O. Rachmaniah, S. Nurkhamidah, N. M. I. P. Suari, and E. N. Prasetyo. "Enhanced Extraction of phenolic compounds from *Moringa oleifera* leaves using

- subcritical water ethanol mixture." In *IOP Conference Series: Materials Science and Engineering*, vol. 543, no. 1, p. 012021. IOP Publishing, 2019. <https://doi.org/10.1088/1757-899X/543/1/012021>
- [14] Mokhtar, Mohamad Aizad Mohd, Roshafima Rasit Ali, Zhongfang Lei, and Zatil Izzah Ahmad Tarmizi. "Banana peels based zinc oxide doped silver nanoparticles for enhanced photocatalytic degradation of paracetamol." In *E3S Web of Conferences*, vol. 516, p. 03003. EDP Sciences, 2024. <https://doi.org/10.1051/e3sconf/202451603003>
- [15] Jafarova, V. N., and G. S. Orudzhev. "Structural and electronic properties of ZnO: A first-principles density-functional theory study within LDA (GGA) and LDA (GGA)+ U methods." *Solid State Communications* 325 (2021): 114166. <https://doi.org/10.1016/j.ssc.2020.114166>
- [16] Soosen Samuel, M., Lekshmi Bose, and K. C. George. "Optical properties of ZnO nanoparticles." *Academic Review* 16 (2009): 57-65.
- [17] Gupta, Rachna, Parth Malik, Nilanjana Das, and Man Singh. "Antioxidant and physicochemical study of Psidium guajava prepared zinc oxide nanoparticles." *Journal of Molecular Liquids* 275 (2019): 749-767. <https://doi.org/10.1016/j.molliq.2018.11.085>
- [18] Jalil, Zulkarnain. "Structural and optical properties of zinc oxide (ZnO) based thin films deposited by sol-gel spin coating method." In *Journal of physics: Conference series*, vol. 1116, no. 3, p. 032020. IOP Publishing, 2018. <https://doi.org/10.1088/1742-6596/1116/3/032020>
- [19] Isa, Eleen Dayana Mohamed. "Pullulan Based Zinc Oxide And Polyaniline Nanocomposites For Photodegradation Of Rhodamine B." (2021).
- [20] Thommes, Matthias, Katsumi Kaneko, Alexander V. Neimark, James P. Olivier, Francisco Rodriguez-Reinoso, Jean Rouquerol, and Kenneth SW Sing. "Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report)." *Pure and applied chemistry* 87, no. 9-10 (2015): 1051-1069. <https://doi.org/10.1515/pac-2014-1117>
- [21] Thommes, Matthias, and Katie A. Cychosz. "Physical adsorption characterization of nanoporous materials: progress and challenges." *Adsorption* 20, no. 2 (2014): 233-250. <https://doi.org/10.1007/s10450-014-9606-z>